

## Test Summary KATUN STANDARD LIFE DRUM TEST

Test Designator: **HP LJ-1200**  
 DRUM: **KATUN STANDARD LIFE**  
 TONER: **KATUN PERFORMANCE**  
 PURPOSE: **SYSTEM TEST**  
 KATUN DRUM P/N: **35160**

DATE: **3/6/2008**  
 TEMP: **23°C**  
 RH: **50± 5**  
 PRINTER: **HEWLETT PACKARD LJ-1200**  
 CARTRIDGE: **OEM - Once Used**

### Image Quality

Section Averages	Density	Background	Character Quality	Vertical Res.	Horizontal Res.
OEM N/N	1.45	0.038%	8.2	62.0	55.5
Test N/N	1.42	0.044%	8.5	68.0	61.5


### Toner Consumption

Test Section	Toner Consumed (g)	mg/copy	Toner Transferred (g)	%Transfer	%Waste	Waste Toner (g)	Copies per Ctg./Btl.	Copies in Section
OEM N/N	119.5	38.5	109.9	92.0%	8.0%	9.6	3636	3100
Test N/N	138.2	41.9	126.4	91.5%	8.5%	11.8	3341	3300


### OPC Coating Loss

Drum Type	Drum Serial #	Total Copies Run	Coating Thickness at Install	Coating Thickness at End	Total Coating Loss	Loss Per 1K copies	Failure mode
OEM N/N	n/a	3,100	32.1	31.8	0.3	0.097	End of Test
Test N/N	n/a	3,300	32.4	32	0.4	0.121	End of Test

### Black Page Image Density

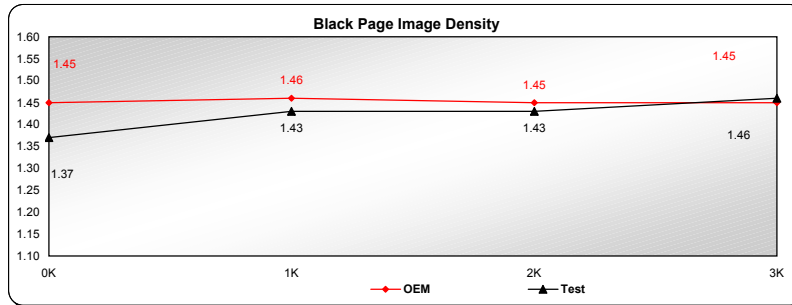

### Halftone Reproductions

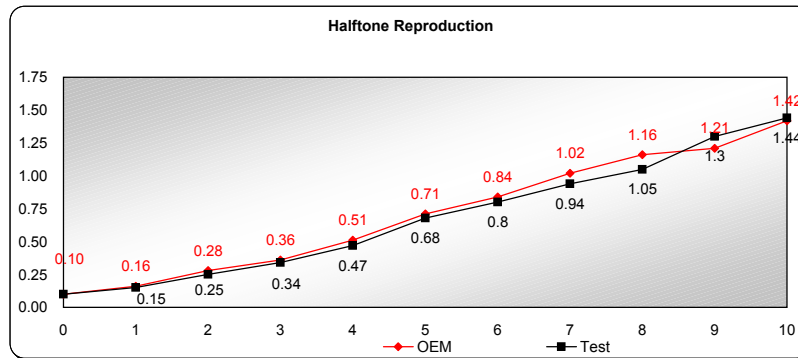

### Background

